



Characterization and potential environmental risks of leachate from shredded rubber mulches

Masakazu Kanematsu^a, Ai Hayashi^b, Michael S. Denison^b, Thomas M. Young^{a,*}

^a Department of Civil and Environmental Engineering, University of California – Davis, CA 95616, United States

^b Department of Environmental Toxicology, University of California – Davis, One Shields Avenue, Davis, CA 95616, United States

ARTICLE INFO

Article history:

Received 22 December 2008

Received in revised form 6 April 2009

Accepted 12 April 2009

Available online 17 May 2009

Keywords:

Shredded rubber mulch

Zinc

Ah receptor activity

Wood mulches

ABSTRACT

In order to determine whether shredded rubber mulches (RM) pose water quality risks when used in stormwater best management practices (BMPs) such as bioretention basins, batch leaching tests were conducted to identify and quantify constituents in leachates from RM such as metal ions, nutrients, total organic carbon (TOC), and aryl hydrocarbon receptor (AhR) activity (determined by the chemically activated luciferase gene expression (CALUX) bioassay) at varied temperature and initial pH values. The results indicate that aqueous extracts of RM contain high concentrations of zinc (Zn) compared with wood mulches (WM), and its concentration increased at lower pH and higher temperature. Although methanol extracts of RM displayed high AhR activity, none of the aqueous extracts of RM had significant activity. Hence, while unknown constituents that have significant AhR activity are present in RM, they appear to be not measurably extracted by water under environmental conditions relevant for stormwater ($5 < \text{pH} < 9$, $10 < T < 40$ °C). Our results suggest that organic constituents in water extracts of RM which have AhR activity may not be of significant concern while leaching of Zn from RM appears to be a potentially larger water quality issue for RM.

© 2009 Elsevier Ltd. All rights reserved.

1. Introduction

Bioretention basins are potential best management practices (BMPs) for removing metals from stormwater (Davis, 2007). Wood mulches (WM) are typically used in these and other types of stormwater BMPs. Although softwood mulches (SWM) are widely available on the west coast, these mulches are not suitable for use in bioretention basins because their low density means that they will not be effectively retained within the basin. Rubber mulches (RM), which are manufactured from used tires, may be a suitable replacement for SWM in bioretention basins due to their higher density and greater resistance to degradation. However, very little information about the bulk chemical composition of RMs or chemical composition in leachate from RMs is available.

Zinc (Zn) has been widely identified as an environmental concern associated with tire wear debris (Hildemann et al., 1991; Councill et al., 2004; Wik and Dave, 2005), which is not surprising given that Zn constitutes approximately 1% by weight of tire rubber (Councill et al., 2004). A significant fraction of Zn was found to leach from tire debris during one year of weathering (Smolders and Degryse, 2002). Elevated concentration of Zn can cause reproductive, developmental, behavioral, and toxic responses in various aquatic organisms (Lefcort et al., 1998; Jelmert and van Leeuwen,

2000). Other studies have found Zn to be the major metal in tire crumb leachate, while other metals including selenium, lead and cadmium were found as minor constituents (Sadiq et al., 1989; Brown, 2007).

Although few investigations of the organic content of leachate from shredded tires have been reported and the results are somewhat inconsistent, it is well known that rubber tire debris contains toxic compounds such as highly aromatic oils and other reactive additives (Ahlbom and Duus, 1994; Wik and Dave, 2005). Exposure of rainbow trout (*Oncorhynchus mykiss*) to tires present in their exposure tanks resulted in elevated ethoxyresorufin-O-deethylase (EROD) activity and mRNA levels of CYP1A1 (Stephensen et al., 2003). These authors concluded that elevation of these activities resulted from exposure of fish to leachate from tires containing highly aromatic oils. The detection of hydroxylated PAH and aromatic nitrogen compounds in the bile of exposed fish suggested PAHs as one of the biggest concerns of RM leachate. Some volatile and semi-volatile organic compounds (carbon disulfide, methyl ethyl ketone, toluene and phenol) were also identified in scrap tire leachates using the TCLP test, although reported levels were far below regulatory limits (Envirologic Inc., 1990). A recent study demonstrated that ground tires released benzothiazole; butylated hydroxyanisole; *n*-hexadecane; and 4-(*t*-octyl) phenol in both the vapor phase and the leachate (Brown, 2007). The 24 h EC₅₀s of rubber pieces toward various aquatic test organisms (*Daphnia magna*, *Pimephales promelas*, *Selenastrum capricornutum*) were determined

* Corresponding author. Tel.: +1 530 754 9399; fax: +1 530 752 7872.
E-mail address: tyoung@ucdavis.edu (T.M. Young).

(Birkholz et al., 2003; Wik and Dave, 2006), and this toxicity was attributed primarily to nonpolar organic compounds (Wik and Dave, 2006). Hence, the organic content of leachate from RM appears to be a significant concern.

The purpose of this study was to determine whether the use of shredded RM for stormwater BMPs or similar applications poses a risk to water quality and to subsequently identify the responsible chemicals. RM and WM extracts were studied in order to identify and quantify constituents (metal ions, nutrients, and total organic carbon (TOC)) that leach out of the RM under various conditions. The presence of Ah receptor (AhR) agonists in the leachate was determined using AhR-dependent chemically-activated luciferase expression (CALUX) bioassay (Denison et al., 2004; Han et al., 2004; Windal et al., 2005), and the organic solvent extract of the RM were analyzed using gas chromatograph mass spectrometry (GC–MS) with full scan mode to identify organic compounds responsible for AhR activity. CALUX is a recombinant cell bioassay that has been used for detection and quantification of dioxin-like chemicals (DLCs), including halogenated aromatic hydrocarbons (HAHs) and polycyclic aromatic hydrocarbons (PAHs), known high affinity AhR agonists (Safe, 1990; Barbach et al., 1992; Wei et al., 1998), as well as diverse array of other chemicals (Seidel et al., 2000; Amakura et al., 2003; Denison et al., 2004; Bohonowych et al., 2008). Since RMs contain toxic compounds such as highly aromatic (HA) oils (Ahlbom and Duus, 1994; Wik and Dave, 2005), it can be expected that extracts of RMs may exhibit significant AhR activity. Taken together, the results of this study will allow evaluation of the potential risk associated with exposure to RM leachate.

2. Materials and methods

2.1. Batch leaching tests

Materials used in this study were RM (West Coast Rubber Recycling), SWM (Ace[®] Cedar Mulch), and HWM (Preen[®] Mulch Plus[®] Hardwood). The experiments employed batch leaching methods with relatively high ratios of mulch mass to water volume ratio (2 g/40 mL = 50 g L⁻¹) and relatively long contact time (3 days). This approach was taken to maximize the detectability of leachate constituents, to allow a wide range of test conditions to be examined and to provide a means of determining which, if any, constituents should be the focus of follow-up studies. The experimental results reported here are likely to represent a “worst case scenario” because any compounds that leach out of the rubber are likely to decline over time as the initial constituent load in the tire particles is leached away (Birkholz et al., 2003) and also because the actual ratio of particle mass to water volume will be lower in most environmental situations. Moreover, the sieved mulches used here had higher specific surface areas than mulches that would be used in the field, potentially allowing more compounds to be leached out. To capture the variable characteristics of stormwater runoff, tests were also conducted at temperatures ranging from 10 to 40 °C (10, 25, and 40 °C) and initial pH values from 5 to 9 (5, 7, and 9).

After drying at 50 °C for 2 days, the mulches were crushed and sieved dry using a 30 mesh U.S. standard sieve (590 µm). Then, 2 g of each mulch was extracted by 40 mL of the synthetic runoff water (SRO, pH 5, 7, or 9), deionized (DI) water, or methanol in 50 mL plastic and glass bottles for 3 days. SROs were prepared to have similar hardness and total dissolved solids concentration as average California stormwater runoff (Kayhanian et al., 2003) using CaSO₄ (34 mg L⁻¹) and NaCl (25.5 mg L⁻¹) and were buffered with 25 mM of potassium hydrogen phthalate (pH 5), sodium bicarbonate (pH 7), or ammonium carbonate (pH 9). The batch contact time was selected as 72 h based on preliminary kinetic studies that sug-

gested that metal leaching from mulch samples was largely complete after this time period. Parallel extractions were performed in plastic and glass bottles to minimize losses of target constituents or input of undesired constituents. The extracts in plastic bottles were used to measure metal ions, nutrients, and pH, and those in glass bottles were used for organic analyses by GC–MS, TOC analyses, and the CALUX bioassay. Samples were diluted as needed to keep constituent concentrations within the quantification range for the relevant analytical instrument following centrifuging and filtering (0.45 µm).

2.2. Digestion tests

The mulches were digested using the HNO₃–H₂O₂ digestion method to quantify metal ion contents. After the pretreatment described in the batch leaching test section, 0.25 g of each mulch sample was digested with 0.5 mL of trace metal grade concentrated nitric acid and 2 mL of 30% hydrogen peroxide for 13 min using microwave heating in 15 mL polyethylene centrifuge tubes. The mixtures were diluted to 15 mL with Milli-Q water before microwave heating. Then, the digests were centrifuged and filtered (0.45 µm) for analyses.

2.3. Analysis of constituents

Metal ion concentrations were measured by inductively coupled plasma mass spectrometry (ICP–MS; Agilent 7500i). All samples were acidified with nitric acid before measurement. Nutrients (NO₃⁻, NH₄⁺, and PO₄³⁻) were measured by flow injection analyzer (FIA; Lachat Quick-Chem). TOC was measured using a TOC analyzer (Shimadzu 5050 TOC with ASI-5000). Since pH 7 and 9 buffers in SRO contain high concentration of inorganic carbon, those samples were thoroughly purged by N₂ gas prior to TOC analysis. The CALUX bioassay was conducted for all aqueous extracts, methanol/water mixture extracts, and methanol extracts to determine the presence of AhR ligands in those extracts. All extracts (2 mL) were evaporated and resuspended in 2 mL of dimethyl sulfoxide (DMSO), and 1 µL of the eluate was analyzed using the CALUX assay. For CALUX analysis, we used recombinant mouse hepatoma (hepa1c1c7) cell lines (H1L1.1c2 and H1L6.1c3), which are identical except for the AhR-responsive luciferase reporter gene they contain (Han et al., 2004). Although both lines respond to AhR agonists with the induction of luciferase activity, the optimal times for induction differ due to subtle differences in the cellular targeting and stability of the two different luciferase reporter gene (Promega). Accordingly, maximal induction times in H1L1.1c2 and H1L6.1c3 cells are 4 and 24 h after treatment, respectively (Han et al., 2004). Experimental procedures for exposing cells and analyzing luciferase activity in these cell lines have been described in detail previously (Han et al., 2004; Bohonowych et al., 2008). To identify AhR agonists in the RM, the methanol extract of RM was dried down and resuspended in 2 mL of hexane and analyzed using an Agilent 6890 gas chromatograph with an Agilent 5973 mass spectrometer (split mode, 5 µL injection at 220 °C, HP19091 J-433 capillary column 30 m by 250 µm i.d. and 0.25 µm thickness, initial oven 60 °C ramped at 30 °C min⁻¹ to 300 °C, then hold 10 min), and the mass spectrometry was performed in electron ionization mode.

3. Results and discussion

3.1. Metal ions and nutrients

Metal ions, nutrients, TOC concentrations, and final pH values in all batch leaching tests are summarized in Table 1 together with

Table 1
Metal ions, nutrients, and TOC concentration in SRO and DI water extracts of mulches (SWM, HWM, and RM) at varied temperature and initial pH.

Mulch	Solution	Temperature (°C)	Initial pH	Final pH	Metal ions (mg L ⁻¹)													Nutrients (mg L ⁻¹)			TOC (mg C L ⁻¹)
					Mg	Al	Cr	Mn	Fe	Cu	Zn	As	Rb	Sr	Ba	Pb	PO ₄ ³⁻ as P	NO ₃ ⁻ as N	NH ₄ ⁺ as N		
RM	Leaching test	SRO	10	5.0	5.1	945 (6.77)	130 (0.6)	0.835 (0.5)	51 (12.2)	541 (0.2)	0 (0.0)	12,483 (5.1)	2.56 (10.4)	2.35 (1.8)	35.1 (17.4)	107 (20.4)	12.10 (2.8)	786	70.8	4290	11
				7.0	8.0	348 (2.49)	0 (0.0)	0.108 (0.1)	21 (5.1)	30 (0.0)	0 (0.0)	4117 (1.7)	0 (0.0)	2.87 (2.2)	15.1 (7.5)	45.1 (8.6)	0 (0.0)	16.6	– ^a	243	87
				9.0	8.9	466 (3.34)	166 (0.8)	0.0273 (0.0)	13 (3.0)	0 (0.0)	0 (0.0)	2544 (1.0)	0.320 (1.3)	3.74 (2.9)	12.8 (6.3)	22.6 (4.3)	1.20 (0.3)	504	49.4	– ^b	86
			25	5.0	5.1	1200 (8.61)	328 (1.5)	3.21 (2.1)	71 (16.9)	827 (0.3)	0 (0.0)	18,930 (7.7)	3.39 (13.8)	6.23 (4.9)	45.9 (22.7)	146 (27.9)	19.3 (4.5)	775	63.2	1060	30
				7.0	7.9	445 (3.19)	1.00 (0.0)	0.594 (0.4)	28 (6.7)	52 (0.0)	0 (0.0)	5597 (2.3)	1.48 (6.0)	4.71 (3.7)	21.6 (10.7)	73.9 (14.1)	0.966 (0.2)	86.1	–	74.3	147
				9.0	8.9	512 (3.67)	122 (0.6)	0.564 (0.4)	14 (3.4)	31 (0.0)	0 (0.0)	2544 (1.0)	0.837 (3.4)	5.27 (4.1)	16.5 (8.2)	29.4 (5.6)	2.56 (0.6)	502	92.4	– ^b	158
		40	5.0	5.1	1180 (8.46)	289 (1.4)	1.96 (1.3)	83 (19.6)	685 (0.2)	4 (2.6)	27,839	2.77 (11.2)	2.52 (2.0)	41.7 (20.6)	149 (28.4)	23 (5.3)	646	63.2	1730	50	
			7.0	8.2	434 (3.12)	0 (0.0)	0.354 (0.2)	24 (5.7)	0 (0.0)	0 (0.0)	3263 (1.3)	1.43 (5.8)	4.14 (3.2)	19.8 (9.8)	42.1 (8.0)	0 (0.1)	138	–	1230	105	
			9.0	8.8	525 (3.76)	97.7 (0.5)	0.743 (0.5)	10 (2.4)	0 (0.0)	0 (0.0)	2082 (0.9)	1.78 (7.2)	5.53 (4.3)	15.7 (7.8)	26.4 (5.0)	1.25 (0.3)	478	31.1	–	111	
		DI water	ER ^c	25	6.3	6.1	395 (2.83)	0 (0.0)	0.948 (0.6)	23 (5.5)	23 (0.0)	0 (0.0)	4542 (1.9)	1.24 (5.0)	3.93 (3.1)	18.5 (9.1)	17.9 (3.4)	0 (0.0)	166	73.6	760
–	–				–	11.3	60.0	59.5	18.0	56.2	1.00	18.9	16.1	16.6	14.5	75.8	84.2	359	–	923	40
Digest ^d	–	–	–	–	2.79 × 10 ²	4.24 × 10 ²	3.09	8.42	5.50 × 10 ³	2.83	4.89 × 10 ³	4.93 × 10 ⁻¹	2.56	4.04	1.05 × 10	8.65	–	–	–	–	
					–	–	–	–	–	–	–	–	–	–	–	–	–	–	–	–	–
SWM	Leaching test	SRO	10	5.0	4.9	34,100 (37.6)	2.13 (0.0)	0.987 (0.4)	680 (32.6)	103 (0.0)	0 (0.0)	48.7 (9.2)	0 (1.4)	26.8 (43.3)	335 (25.4)	192.2 (8.9)	0 (0.0)	8890	<1	208	263
				7.0	7.9	16,300 (18.0)	0 (0.0)	1.59 (0.7)	98 (4.7)	81 (0.0)	0 (0.0)	7.08 (1.3)	0 (0.0)	32.2 (52.1)	117 (8.8)	65.0 (3.0)	0 (0.0)	8530	–	142	347
				9.0	8.1	11,800 (13.0)	0 (0.0)	11.7 (5.2)	20 (1.0)	185 (0.0)	0 (0.0)	0 (0.0)	0 (0.0)	0 (0.0)	33.6 (54.4)	81.9 (6.2)	44.6 (2.1)	0 (0.0)	7270	<1	–
			25	5.0	5.0	43,300 (47.7)	122 (0.6)	2.41 (1.1)	789 (37.8)	87 (0.0)	0 (0.0)	100 (18.9)	4.40 (29.3)	33.8 (54.6)	443 (33.6)	255 (11.8)	0.185 (0.2)	9250	<1	243	252
				7.0	7.5	17,400 (19.2)	47.9 (0.2)	1.52 (0.7)	110 (5.3)	37 (0.0)	1 (0.3)	21.2 (4.0)	3.50 (23.3)	31.8 (51.4)	137 (10.4)	72.8 (3.4)	0.100 (0.1)	8610	–	317	297
				9.0	8.1	12,500 (13.8)	61.4 (0.3)	1.61 (0.7)	29 (1.4)	61 (0.0)	0 (0.0)	20.7 (3.9)	3.91 (26.0)	31.3 (50.5)	100 (7.6)	54.4 (2.5)	0.142 (0.2)	6730	<1	–	435
		40	5.0	4.9	39,100 (43.1)	100 (0.5)	5.02 (2.2)	690 (33.1)	84 (0.0)	45 (24.8)	133 (25.3)	5.22 (34.8)	30.8 (49.8)	408 (30.9)	227 (10.5)	4.37 (5.5)	8610	<1	827	267	
			7.0	7.8	8490 (9.4)	71.8 (0.3)	3.40 (1.5)	12 (0.6)	286 (0.1)	41 (22.8)	13.4 (2.5)	3.40 (22.7)	25.1 (40.5)	59.3 (4.5)	34.1 (1.6)	1.64 (2.1)	6890	–	750	614	
			9.0	8.1	11,500 (12.7)	38.4 (0.2)	2.18 (1.0)	52 (2.5)	145 (0.0)	11 (6.1)	13.2 (2.5)	4.00 (26.7)	28.9 (46.7)	84.5 (6.4)	49.1 (2.3)	0.510 (0.6)	7880	<1	–	498	
		DI water	ER ^c	25	6.3	5.9	12,000 (13.2)	68.4 (0.3)	2.50 (1.1)	137 (6.5)	65 (0.0)	1 (0.3)	25.3 (4.8)	4.94 (32.9)	26.4 (42.7)	85.2 (6.5)	45.3 (2.1)	0 (0.1)	11,100	<1	262
–	–				–	31.0	42.9	64.4	24.1	73.5	19.2	19.1	41.0	16.9	37.8	37.8	7.72	28.9	–	17.1	19
Digest ^d	–	–	–	–	1.81 × 10 ³	4.42 × 10 ²	4.53	4.17 × 10	1.04 × 10 ⁴	3.83	1.05 × 10	1.80 × 10 ⁻¹	1.24	2.64 × 10	4.33 × 10	1.60	–	–	–	–	
					–	–	–	–	–	–	–	–	–	–	–	–	–	–	–	–	–
HWM	Leaching test	SRO	10	5.0	5.1	49,000 (41.4)	1170 (0.8)	36.1 (2.6)	4150 (47.4)	877 (0.0)	46 (2.4)	301 (17.8)	257 (32.6)	149 (34.2)	666 (36.1)	265 (9.3)	23.2 (1.6)	11,744	<1	815	563
				7.0	7.6	17,700 (15.0)	295 (0.2)	25.1 (1.8)	765 (8.7)	599 (0.0)	32 (1.7)	48.0 (2.8)	213 (27.0)	135 (31.1)	190 (10.3)	54.2 (1.9)	3.41 (0.2)	7873	–	107	665
				9.0	8.0	11,000 (9.3)	315 (0.2)	28.6 (2.0)	479 (5.5)	976 (0.0)	32 (1.7)	28.1 (1.7)	181 (23.0)	123 (28.2)	131 (7.1)	36.2 (1.3)	4.43 (0.3)	6873	<1	–	653
			25	5.0	5.2	58,400 (49.4)	1470 (1.0)	47.0 (3.3)	4415 (50.4)	1186 (0.0)	58 (3.1)	333 (19.7)	270 (34.3)	150 (34.4)	722 (39.2)	312 (10.9)	29.9 (2.0)	11,657	<1	1290	630
				7.0	7.4	19,000 (16.1)	578 (0.4)	36.5 (2.6)	946 (10.8)	812 (0.0)	50 (2.7)	80.2 (4.7)	237 (30.1)	145 (33.3)	218 (11.8)	73.3 (2.6)	8.87 (0.6)	7369	–	1780	638
				9.0	7.8	17,800 (15.1)	734 (0.5)	42.9 (3.0)	875 (10.0)	740 (0.0)	100 (5.4)	84.1 (5.0)	275 (34.9)	144 (33.2)	209 (11.4)	65.0 (2.3)	14.9 (1.0)	7709	<1	–	723
		40	5.0	5.3	57,800 (48.9)	1320 (0.9)	63.8 (4.5)	4715 (53.8)	2410 (0.1)	90 (4.8)	364 (21.4)	335 (42.5)	157 (36.0)	774 (42.0)	359 (12.6)	29.1 (2.0)	13,938	<1	828	680	
			7.0	7.9	17,800 (15.1)	576 (0.4)	40.5 (2.9)	812 (9.3)	843 (0.0)	70 (3.7)	114 (6.7)	275 (34.9)	142 (32.6)	195 (10.6)	66.4 (2.3)	8.96 (0.6)	9422	–	696	740	
			9.0	7.8	14,500 (12.3)	743 (0.5)	48.4 (3.4)	706 (8.1)	1042 (0.0)	99 (5.3)	62.8 (3.7)	270 (34.3)	142 (32.6)	182 (9.9)	61.7 (2.2)	14.4 (1.0)	10,461	<1	–	853	
		DI water	ER ^c	25	6.3	6.0	28,000 (23.7)	909 (0.6)	37.3 (2.6)	1575 (18.0)	889 (0.0)	45 (2.4)	153 (9.1)	255 (32.4)	88.3 (20.3)	281 (15.2)	78.6 (2.7)	12.8 (0.9)	10,494	11	182
–	–				–	47.4	57.4	2.2	66.5	9.4	10.4	91.3	7.5	39.1	28.7	7.2	44.8	42.4	–	89.8	16.5
Digest ^d	–	–	–	–	2.36 × 10 ³	2.87 × 10 ³	2.83 × 10	1.75 × 10 ²	4.97 × 10 ⁴	3.74 × 10	3.39 × 10	1.58 × 10	8.70	3.69 × 10	5.73 × 10	2.99 × 10	–	–	–	–	
					–	–	–	–	–	–	–	–	–	–	–	–	–	–	–	–	–

Values in parentheses represent the fraction of the total concentration leached out during the batch testing.

^a Samples not analyzed for a parameter are indicated by (–).

^b Because of buffer solution composition or impurities, no results for NO₃⁻ concentration are presented for any of the pH 7 synthetic runoff extractions and no NH₄⁺ concentration data are available for the pH 9 synthetic runoff samples.

^c Extraction reproducibility (ER) was estimated as the relative percent difference between SRO extracts (pH 7, 25 °C) and the corresponding DI water extracts using the following equation: $ER = \left| \frac{SRO\ extract - DI\ extract}{SRO\ extract} \right| \times 100$.

^d Unit: μg g⁻¹.

total metal ion concentrations in the mulches (unit: $\mu\text{g g}^{-1}$) determined by the digestion tests and the calculated leaching fraction. Since the digestion tests confirmed that Zn concentrations in the RM were significantly higher than those in SWM or HWM, it is not surprising that high concentrations of Zn (2000–28,000 $\mu\text{g L}^{-1}$) were detected in RM extracts. The extracted Zn concentrations were generally higher at lower pH as would be expected from the generally higher desorption or dissolution of metals under acidic conditions (Table 1, Fig. 1). At pH 5 there was also an obvious trend toward increased Zn concentration with temperature (Fig. 1). Zn concentrations in RM were higher than those in SWM and HWM by a factor 40–200 (Table 1). The observed concentrations of Zn in leachates are generally consistent with those from previous studies of rubber tire debris (Wik and Dave, 2006; Brown, 2007). Besides, given tire-tread material has a Zn content of approximately 1 wt% (Councell et al., 2004), approximately 50% of Zn in RM appeared to be extracted in the digestion tests (Table 1). The calculated leaching fraction of Zn based on our extraction results, however, was less than approximately 10% in any scenario. The calculated leaching fractions of almost all metal ions for RM were also relatively lower than those for WM. These results imply that metal ions contained inside RM particles are less readily leached out than for WM due to higher resistance to degradation. Chromium (Cr), copper (Cu), and lead (Pb) concentrations in RM extracts were below detection in almost all cases. Concentrations of Mg, Mn, As, Rb, Sr, and Ba in RM samples were almost always lower than those in WM samples at the corresponding pH and temperature. The concentrations of Fe and Al, which are major crustal components, were higher in the HWM extracts than in the RM extracts but these are not typically of water quality concern. Concentrations for almost all metals from the mulches were highest at the lowest pH (pH 5) and the highest temperature (40 °C) studied.

Nutrient concentrations in the leachate samples are also summarized in Table 1. Nitrate (NO_3^-) was detected in RM extracts (30–92 $\mu\text{g L}^{-1}$ as N), but was not detectable in SWM and HWM extracts except for a single extraction using water. While ammonium concentrations in RM extracts were similar to or greater than those for the WM samples at pH 5 or 7, no clear concentration trend was observed with varying temperature and pH. High concentrations of PO_4^{3-} (6700–14,000 $\mu\text{g L}^{-1}$ as P) were detected in SWM and HWM extracts and concentrations tended to decline as pH was increased. Since PO_4^{3-} levels in RM extracts were far lower (<800 $\mu\text{g L}^{-1}$ as P), PO_4^{3-} leaching from RM would not be a significant concern.

Although the batch leaching tests were unfortunately conducted without replication, the extraction reproducibility (ER)

was estimated as the relative percentage difference between SRO extraction (pH 7, 25 °C) and the DI water extraction using the formula shown in the footnote of Table 1. For almost all metal ions, the ERs were less than 100, and the effects of initial pH, temperature and mulch type were much larger than the ER values.

3.2. TOC and organic compounds

The TOC concentrations in the extracts were highest for WM (Table 1). The SWM and HWM extracts were yellowish and blackish, respectively, so the high TOC concentration probably derived from natural organic matter including humic and fulvic acids. Basic conditions are employed to extract humic materials from soils or sediments so it is not surprising that the TOC concentrations generally increased with increasing extraction pH. The acidic nature of the extracted organic materials in the WM was further confirmed by the relatively large decrease in initial pH observed for extractions starting with the highest pH (Table 1). The pH of the HWM extracts decreased from 9 to below 8 at all temperatures, while the decrease for SWM was somewhat smaller. These changes are directly correlated with TOC levels in the extracts. TOC concentrations in the RM extracts were always much lower (10–160 mg L^{-1}) compared to (252–853 mg L^{-1}) in the WM extracts.

3.3. AhR activity

Analysis of the extracts for the presence of AhR agonists was carried out using recombinant mouse hepatoma (hepa1c1c7) cell lines (H1L1.1c2 and H1L6.1c3), containing an AhR-responsive luciferase reporter gene. The differential cell targeting and stability of the two slightly different luciferase reporter gene products (resulting from selected mutation in the luciferase gene) in these two cell lines facilitate detection and characterization of metabolically labile AhR agonists. The gene induction response in H1L1.1c2 cells is greatly enhanced at 4 h after AhR agonist treatment and suppressed at 24 h (Garrison et al., 1996; Han et al., 2004), while the more stable luciferase in H1L6.1c3 cells accumulates over 24 h and can allow characterization of more metabolically stable AhR agonists (Han et al., 2004). The level of luciferase activity in H1L6.1c3 cells at 4 h is relatively low (compared to the H1L1.1c2 cells) and as such, it is not particularly useful for detection and characterization of metabolically labile AhR agonists. Accordingly, since the only difference between these cells is that of the stability of the luciferase gene product, these cell lines have been used extensively to detect and differentiate between metabolically

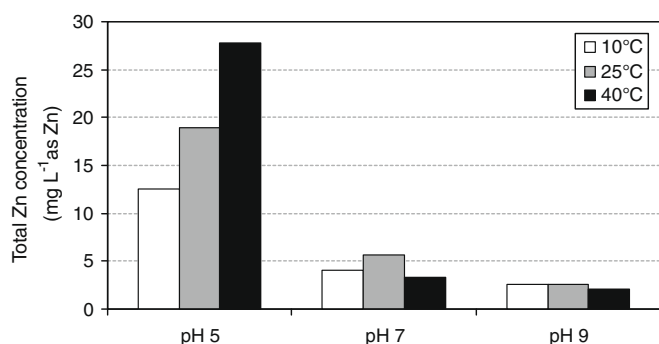


Fig. 1. Total Zn concentration in SRO extracts from RM at varied temperature and initial pH. The batch contact time was selected as 72 h. All SROs were prepared using CaSO_4 (34 mg L^{-1}) and NaCl (25.5 mg L^{-1}) and were buffered with 25 mM of potassium hydrogen phthalate (pH 5), sodium bicarbonate (pH 7), or ammonium carbonate (pH 9). Total Zn includes both inorganic Zn and organo-Zn. The digestion test result showed that total Zn concentration in RM was 4.89 mg g^{-1} as Zn equivalent to 244.5 mg L^{-1} in the leaching test tubes.

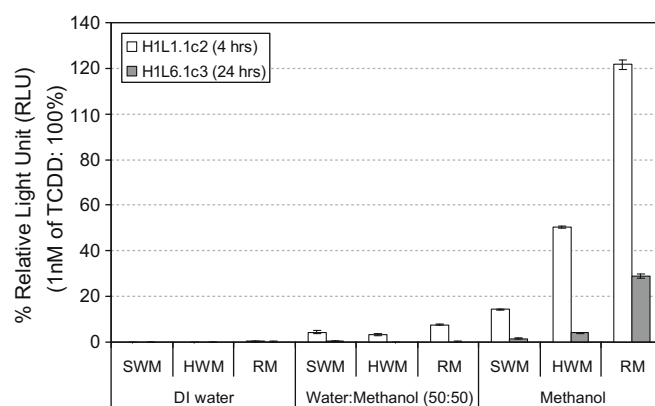


Fig. 2. Induction of AhR-dependent luciferase reporter gene expression in H1L1.1c2 and H1L6.1c3 cells by DI water extracts, water/methanol mixture extracts (50:50), and methanol extracts of mulches (SWM, HWM, and RM). Percent RLU of all method blanks were less than 2% and 1% for H1L1.1c2 and H1L6.1c3, respectively. Percent RLU results are presented as an average \pm SD of triplicate incubations.

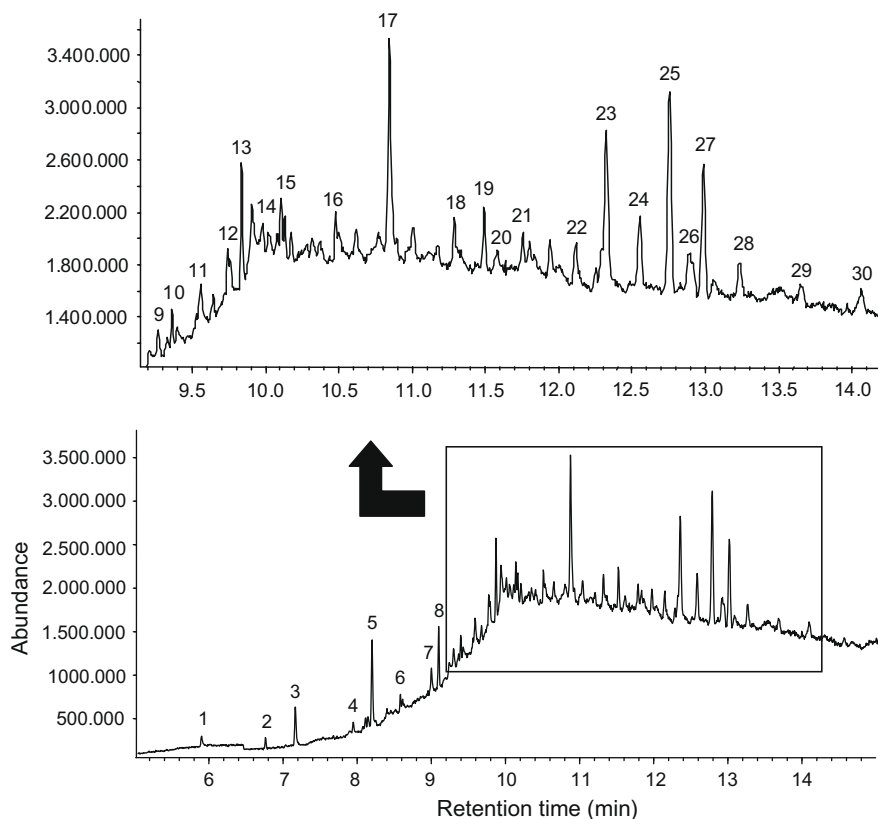


Fig. 3. GC–MS chromatogram of the methanol extract of RM transferred into hexane. The peak numbers shown in this figure correspond to the numbers in Table 2.

Table 2

Organic compounds identified in RM extracts by GC–MS analyses and NIST-library. The numbers correspond to the peak numbers in Fig. 3.

No.	Compound
1	Benzothiazole
2	Pyrazole
3	o-Cyanobenzoic acid
4	Diphenylamine
5	2(3H)-Benzothiazolone
6	Optadecane, Heptadecane
7	Nonadecane
8	Hexadecanoic acid, methyl ester
9	2-Phenylbenzimidazole
10	Tetracosane
11	Benzothiazole, 2-phenyl-
12	Hemeicosane
13	Octadecanoic acid, methyl ester
14	9,10-Anthracenedione, 2-ethyl-
15	Eicosane
16	Tricosane
17	Pyrimidine, 2-(4-pentylphenyl)-5-propyl-
18	Pentacosane
19	Bis(2-ethylhexyl) phthalate
20	Cycloninasiloxane, octadecamethyl-
21	Hexacosane
22	Benzenamine
23	1-Phenanthrenecarboxylic acid, 1,2,3,4,4
24	1,4-Benzenediamine, N,N'-diphenyl-
25	1,1'-Biphenyl, 4, 4', 5', 6'-tetramethoxy-
26	Phenol, 2,4-bis(1-methyl-1-phenylethyl)-
27	7-Hydroxybenzo[flavone
28	Docosanoic acid
29	Dotriacontane
30	Naphthalene, 2-(bromomethyl)-

labile and stable AhR agonists and extracts containing such chemicals (Garrison et al., 1996; Gebremichael et al., 1996; Seidel et al., 2000, 2001; Ziccardi et al., 2000; Denison et al., 2004). While sig-

nificant induction of AhR dependent luciferase activity was observed at 4 h after treatment in H1L1.1c2 cells by all methanol extracts (with RM > HWM > SWM (Fig. 2)), maximal induction was only observed with the RM extract. Thus, while each extract contains AhR agonists, the RM extract contained the greatest concentration of and/or most efficacious AhR agonists. These results combined with the lack of luciferase induction by the water extracts and the very low level of induction (<10% of TCDD) by the water:methanol (50:50) extracts indicates that the induction results from a nonpolar chemical(s) in the extract. Comparison of the level of induction by each extract at 4 and 24 h after treatment revealed that all three extracts were significantly less potent at the later time point (Fig. 2), consistent with the induction being by metabolically labile chemicals. A time-dependent decrease in the overall level of luciferase induction has been observed previously and results from metabolism of the inducing chemical by the cells into AhR inactive forms (Machala et al., 2001; Nagy et al., 2002; Han et al., 2004; Bohonowych et al., 2008). The reduction in luciferase gene induction at 24 h also demonstrates that the responsible AhR active chemicals in the extract were not HAHs, as these chemicals are resistant to metabolic degradation and thus are persistent activators of AhR-dependent gene expression (Ziccardi et al., 2000; Denison et al., 2004).

3.4. GC–MS analysis

Since the methanol extract of RM showed the highest AhR activity, it was transferred into hexane at a concentration factor of one with the original methanol extract and injected into the GC–MS. The GC–MS chromatogram of the eluate is shown in Fig. 3, and the National Institute of Standards and Technology (NIST) mass spectral library was used to provide information about the identity of compounds in the eluate (Table 2). Benzenoid aromatic

compounds such as benzothiazole, long chain alkyl groups, and their derivatives were detected. Benzothiazole and their derivatives are typical compounds contained in tires (Kumata et al., 2000). Since the extract is a complex mixture and concentrations of those compounds are unknown, it is not possible to conclude that these listed compounds are responsible for the high AhR activity in the methanol extract of RM. It is, however, possible that these compounds were responsible for the high AhR activity in the methanol extract of RM.

4. Conclusions

- Aqueous extracts of RM contain high concentration of one metal, Zn compared to extracts of WMs. Leaching of Zn from RM therefore appears to represent the most significant water quality concern associated with specification of these materials for use in BMPs.
- Extracts of RM contained similar concentrations of nitrate and ammonium and lower concentrations of phosphate and TOC than the WM extracts.
- Aqueous extracts of RM or WMs contained little or no AhR activity as measured by the CALUX bioassay.
- Organic solvent extracts of RM and SWM induced significant levels of AhR-dependent gene expression indicating the presence of AhR active nonpolar chemicals, and the presence of these activators in both materials.
- The transient nature of the CALUX induction response (i.e. lower at 24 h) indicates that the responsible AhR active chemicals were not HAHs, as these latter chemicals are metabolically stable and induce persistent activation of gene expression.
- Although the CALUX bioassay results are not a substitute for whole organism toxicity testing, they suggest that the organic constituents leached from RM may not be of significant concern under most environmental conditions relevant to stormwater.
- Benzenoid aromatic compounds, long chain alkyl groups, and their derivatives were detected in the methanol extracts transferred into hexane and analyzed by GC–MS, and these compounds may contribute to the high AhR activity present in these materials.
- The suitability of RM in stormwater BMP applications is therefore highly dependent on the susceptibility of the receiving water to negative consequences from additional Zn inputs and must be evaluated on a site specific basis.

Acknowledgments

The project described was supported in part by Grant Number P42ES004699 from the National Institute of Environmental Health Sciences and in part under Contract 43A0168 from the California Department of Transportation. The content is solely the responsibility of the authors and does not necessarily represent the official views of the organizations above. Analytical assistance and advice from Peter G. Green, Wei-Hsiang Chen, and Brett Harvey are gratefully acknowledged.

References

Ahlbom, J., Duus, U., 1994. Nya hjulspår – en produktstudie av gummidäck (New Wheel Tracks – a product study of rubber tyres). KEMI National Chemicals Inspectorate, 78.

Amakura, Y., Tsutsumi, T., Sasaki, K., Yoshida, T., Maitani, T., 2003. Screening of the inhibitory effect of vegetable constituents on the aryl hydrocarbon receptor-mediated activity induced by 2,3,7,8-tetrachlorodibenzo-*p*-dioxin. *Biological & Pharmaceutical Bulletin* 26, 1754–1760.

Barbach, K.M., Poland, A., Bradfield, C.A., 1992. Cloning of the Ah-receptor cDNA reveals a distinctive ligand-activated transcription factor. *Proceedings of the National Academy of Sciences of the United States of America* 89, 8185–8189.

Birkholz, D.A., Belton, K.L., Guidotti, T.L., 2003. Toxicological evaluation for the hazard assessment of tire crumb for use in public playgrounds. *Journal of the Air & Waste Management Association* 53, 903–907.

Bohonowych, J.E.S., Zhao, B., Timme-Laragy, A., Jung, D., Di Giulio, R.T., Denison, M.S., 2008. Newspapers and newspaper ink contain agonists for the Ah receptor. *Toxicological Sciences* 102, 278–290.

Brown, D.R., 2007. Artificial Turf Exposures to Ground-up Rubber Tires Athletic Fields/Playgrounds/Gardening Mulch. Environment and Human Health, Inc., North Haven, CT.

Council, T.B., Duckenfield, K.U., Landa, E.R., Callender, E., 2004. Tire-wear particles as a source of zinc to the environment. *Environmental Science & Technology* 38, 4206–4214.

Davis, A.P., 2007. Field performance of bioretention: Water quality. *Environmental Engineering Science* 24, 1048–1064.

Denison, M.S., Zhao, B., Baston, D.S., Clark, G.C., Murata, H., Han, D., 2004. Recombinant cell bioassay systems for the detection and relative quantitation of halogenated dioxins and related chemicals. *Talanta* 63, 1123–1133.

Envirologic Inc., 1990. A Report on the use of Shredded Scrap Tires in on-site Sewage Disposal Systems. Department of Environmental Conservation, State of Vermont, Brattleboro, VT.

Garrison, P.M., Tullis, K., Aarts, J.M.M.J.G., Brouwer, A., Giesy, J.P., Denison, M.S., 1996. Species-specific recombinant cell lines as bioassay systems for the detection of 2,3,7,8-tetrachlorodibenzo-*p*-dioxin-like chemicals. *Fundamental and Applied Toxicology* 30, 194–203.

Gebremichael, A., Tullis, K., Denison, M.S., Cheek, J.M., Pinkerton, K.E., 1996. Ah-receptor-dependent modulation of gene expression by aged and diluted sidestream cigarette smoke. *Toxicology and Applied Pharmacology* 141, 76–83.

Han, D., Nagy, S.R., Denison, M.S., 2004. Comparison of recombinant cell bioassays for the detection of Ah receptor agonists. *Biofactor* 20, 11–22.

Hildemann, L.M., Markowski, G.R., Cass, G.R., 1991. Chemical-composition of emissions from urban sources of fine organic aerosol. *Environmental Science & Technology* 25, 744–759.

Jelmert, A., van Leeuwen, J., 2000. Harming local species or preventing the transfer of exotics? Possible negative and positive effects of using zinc anodes for corrosion protection of ballast water tanks. *Water Research* 34, 1937–1940.

Kayhanian, M., Singh, A., Borroum, S., 2003. Impact of annual average daily traffic on highway runoff pollutant concentration. *Journal of Environmental Engineering* 129 (11), 975–990.

Kumata, H., Sanada, Y., Takada, H., Ueno, T., 2000. Historical trends of N-cyclohexyl-2-benzothiazolamine, 2-(4-morpholinyl)benzothiazole, and other anthropogenic contaminants in the urban reservoir sediment core. *Environmental Science & Technology* 34, 246–253.

Lefcort, H., Meguire, R.A., Wilson, L.H., Ettinger, W.F., 1998. Heavy metals alter the survival, growth, metamorphosis, and antipredatory behavior of Columbia spotted frog (*Rana luteiventris*) tadpoles. *Archives of Environmental Contamination and Toxicology* 35, 447–456.

Machala, M., Ciganek, M., Blaha, L., Minksova, K., Vondrack, J., 2001. Aryl hydrocarbon receptor-mediated and estrogenic activities of oxygenated polycyclic aromatic hydrocarbons and azaarenes originally identified in extracts of river sediments. *Environmental Toxicology and Chemistry* 20, 2736–2743.

Nagy, S.R., Sanborn, J.R., Hammock, B.D., Denison, M.S., 2002. Development of a green fluorescent protein-based cell Bioassay for the rapid and inexpensive detection and characterization of Ah receptor agonists. *Toxicological Sciences* 65, 200–210.

Sadiq, M., Alam, I., Elmubarek, A., Almohdhar, H.M., 1989. Preliminary evaluation of metal pollution from wear of auto tires. *Bulletin of Environmental Contamination and Toxicology* 42, 743–748.

Safe, S., 1990. Polychlorinated biphenyls (PCBs), dibenzo-*p*-dioxins (PCDDs), dibenzofurans (PCDFs), and related compounds: Environmental and mechanistic considerations which support the development of toxic equivalency factors (TEFs). *Critical Reviews in Toxicology* 21, 51–88.

Seidel, S.D., Li, V., Winter, G.M., Rogers, W.J., Martinez, E.I., Denison, M.S., 2000. Ah receptor-based chemical screening bioassays: application and limitations for the detection of Ah receptor agonists. *Toxicological Sciences* 55, 107–115.

Seidel, S.D., Winters, G.M., Rogers, W.J., Ziccardi, M.H., Li, V., Keser, B., Denison, M.S., 2001. Activation of the Ah receptor signaling pathway by prostaglandins. *Journal of Biochemical and Molecular Toxicology* 15, 187–196.

Smolders, E., Degryse, F., 2002. Fate and effect of zinc from tire debris in soil. *Environmental Science & Technology* 36, 3706–3710.

Stephens, E., Adolfsson-Erici, M., Celander, M., Hulander, M., Parkkonen, J., Hegelund, T., Sturve, J., Hasselberg, L., Bengtsson, M., Forlin, L., 2003. Biomarker responses and chemical analyses in fish indicate leakage of polycyclic aromatic hydrocarbons and other compounds from car tire rubber. *Environmental Toxicology and Chemistry* 22, 2926–2931.

Wei, Y.D., Helleberg, H., Rannug, U., Rannug, A., 1998. Rapid and transient induction of CYP1A1 gene expression in human cells by the tryptophan photoproduct 6-formylindolo[3,2-*b*]carbazole. *Chemico-Biological Interactions* 110, 39–55.

Wik, A., Dave, G., 2005. Environmental labeling of car tires – toxicity to *Daphnia magna* can be used as a screening method. *Chemosphere* 58, 645–651.

Wik, A., Dave, G., 2006. Acute toxicity of leachates of tire wear material to *Daphnia magna* – variability and toxic components. *Chemosphere* 64, 1777–1784.

Windal, I., Denison, M.S., Birnbaum, L.S., Van Wouwe, N., Baeyens, W., Goeyens, L., 2005. Chemically activated luciferase gene expression (CALUX) cell bioassay analysis for the estimation of dioxin-like activity: critical parameters of the CALUX procedure that impact assay results. *Environmental Science & Technology* 39, 7357–7364.

Ziccardi, M.H., Gardner, I.A., Denison, M.S., 2000. Development and modification of a recombinant cell bioassay to directly detect halogenated and polycyclic aromatic hydrocarbons in serum. *Toxicological Sciences* 54, 183–193.